

AD-A267 820



FASTC-ID(RS)T-0101-93

**FOREIGN AEROSPACE SCIENCE AND  
TECHNOLOGY CENTER**

**DTIC**  
**ELECTE**  
**AUG 11 1993**  
**S A D**



CIRCULAR POLARIZING MIRRORS FOR HIGH POWER LASERS

by

Chen Qingming, Zhou Fengqing, et al.



Approved for public release;  
Distribution unlimited.

425  
039

**93-18419**



93

123

## HUMAN TRANSLATION

FASTC-ID(RS)T-0101-93 16 July 1993

MICROFICHE NR: 93C000459

CIRCULAR POLARIZING MIRRORS FOR HIGH POWER LASERS

By: Chen Qingming, Zhou Fengqing, et al.

English pages: 10

Source: Unknown; pp. 193-196

Country of origin: China

Translated by: SCITRAN

F33657-84-D-0165

Requester: FASTC/TATD/Bruce Armstrong

Approved for public release; Distribution unlimited.

THIS TRANSLATION IS A RENDITION OF THE ORIGINAL FOREIGN TEXT WITHOUT ANY ANALYTICAL OR EDITORIAL COMMENT STATEMENTS OR THEORIES ADVOCATED OR IMPLIED ARE THOSE OF THE SOURCE AND DO NOT NECESSARILY REFLECT THE POSITION OR OPINION OF THE FOREIGN AEROSPACE SCIENCE AND TECHNOLOGY CENTER.

PREPARED BY:

TRANSLATION DIVISION  
FOREIGN AEROSPACE SCIENCE AND  
TECHNOLOGY CENTER  
WPAFB, OHIO

# GRAPHICS DISCLAIMER

All figures, graphics, tables, equations, etc. merged into this translation were extracted from the best quality copy available.

Accession For	
NTIS	CRA&I <input checked="" type="checkbox"/>
DTIC	TAB <input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution	
Availability Codes	
Dist	Avail and/or Special
A-1	

DTIC QUALITY INSPECTED 3

FASTC-ID(RS)T-0101-93

## Circular Polarizing Mirrors for High Power Lasers

Chen Qingming, Zhou Fengqing, Li Xiaoping, He Yonggui, Wang  
Jinhua

(National Laboratory of Laser Technology, HUST)

**Abstract** In this paper, the circular polarizing mirrors for high power lasers have been theoretically and experimentally studied, the circular polarizing mirror coated with multiple-film, which could induce 90 degrees phase retardation is prepared experimentally.

### I. Introduction

Long after the high power lasers were introduced to industrial manufacturing, attention has been paid only to the effect of power, mode, speck dimension after focusing, and auxiliary gas of the laser beam on the speed and quality of industrial manufacturing, while the effect of polarization of the laser beam was rarely studied. It was generally thought that, during the manufacturing process, the input laser beams on the surface of the work piece followed the normal direction and there was no relationship between the polarization and the coupling of laser beam energy in the material. In early 1980's, it was discovered by Olsen of Denmark Institute of Technology that during the laser cutting process, the assumption that laser beam entered into the material along the normal direction was only

correct in the initial reaction period. Once the cut was formed, the laser beam would skim through the surface of the work piece. Because of this reason, the reflection and absorption of laser beam by the material was strongly affected by the polarization of the laser beam.[1] For example, when laser was used in cutting or welding, the width of the cut or weld is different along different directions and the slanting of the cut or weld seam was determined by the polarization of the laser beam. Not only is polarization an important factor in laser manufacturing, it is sometimes the determining factor. After extensive study in the 1980's, the circular polarizing light was found to be the best light in operations such as cutting or welding. Circular polarizing light can not only expedite manufacturing speed, optimize manufacturing quality, it can also be used to solve many manufacturing problems not achievable with other lights.

The key element in obtaining circular polarizing light is the manufacturing of circular polarizing mirror. In this paper, the theoretical calculation and experimental manufacturing of circular polarizing mirror is studied.

## II. Theoretical analysis and calculation

The best way to obtain circular polarizing light was to use polarizing element in the laser resonance cavity so that linear polarizing light can be output without loss of efficiency and power; and to use circular polarizing mirror to convert linear polarizing light to circular polarizing light with basically the

same power density. The effect of circular polarizing mirror is somewhat like that of a quarter-wavelength mirror. Modern industrial manufacturing lasers are operating in the infrared range with optical power density on the order of 500W. At present, the infrared material capable of high power operation and significant double-refraction does not exist. Therefore, high power infrared laser devices could not use transmission-type quarter-wavelength mirror. As a result, multiple-film reflection devices, called circular polarizing mirror in this paper, were proposed.[2] The theoretical design and experimental manufacturing of a high power circular polarizing mirror with center wavelength  $10.6\mu\text{m}$  is discussed in this paper. The design principle and manufacturing method can be used in circular polarizing mirrors with other center wavelengths.

The design requirements of a circular polarizing mirror are:

- 1) When the incident angle is  $\theta_i = 45^\circ$  ( $\theta_i$  is the actual incident angle), the linear polarizing light will be decomposed into two mutually perpendicular vectors S and P waves with identical amplitude and frequency and zero phase retardation on the plane of the mirror.
- 2) After reflection by thin film circular polarizing mirror, the two components of the output light would have equal amplitude and maintain the same magnitude as the input light while the phase retardation of S and P waves  $\pm\Delta\phi$  was  $90^\circ$ . (If the left or right rotation was not distinguished than the phase retardation will be  $90^\circ$ .) In this manner, the output light would be basically circular polarizing light without energy loss.

Based on these requirements, the ideal laser polarizing mirror should satisfy the following two necessary conditions:

1. The reflectivity of mirror with respect to S and P waves should be basically equal and approaching 1; namely,  $R_s \approx R_p \approx 1$ .

2. The phase retardation with respect to S and P waves should be  $90^\circ$ ; namely,  $\Delta\phi = \phi_s - \phi_p \approx 90^\circ$ . Because of manufacturing technology the actual optical multiple-film device will deviate from these ideal conditions.

The structure of circular polarizing mirror is: the substrate material was single crystal  $\text{GaAs}$  and the base film material was Au or Ag; the medium film material was  $\text{BaF}_2$  and  $\text{ZnSe}$ ; the number of layers of medium film are both even numbers with high and low reflectivities alternating and the film in contact with the metallic base film was a low reflectivity material. The numbers of medium films used in this study were 10, 12 and 14. When the number of layers increased, the reflection band around  $\Delta\phi = 90^\circ$  was wider. However, too many layers would result in a low overall reflectivity because of absorption and scattering.

The equations and symbols for theoretical calculation of circular polarizing mirror were the same as in reference [3]. The characteristic matrix of the film system is

$$\begin{pmatrix} B \\ C \end{pmatrix} = \left[ \prod_{j=1}^K \begin{pmatrix} \cos\delta_j & \frac{i}{\eta_j} \sin\delta_j \\ i\eta_j \sin\delta_j & \cos\delta_j \end{pmatrix} \right] \begin{pmatrix} 1 \\ \eta_{k+1} \end{pmatrix} \quad (1)$$

For S and P waves, the phase thickness of the film layer is

$$\delta_i = \frac{2\pi}{\lambda} N_i d_i \cos \theta_i \quad (2)$$

The angle of refraction  $\theta_i$  is determined by refractivity.

Conductance  $\eta_i$  is determined by the following equations

$$\eta_i = \begin{cases} N_i \cos \theta_i & \text{S wave} \\ N_i / \cos \theta_i & \text{P wave} \end{cases} \quad (3)$$

where  $N_j$  is the refractivity of the  $j$ -th layer material.

Considering absorption and metallic base film,  $N_j$  is usually even. The composite conductance of multiple-layer medium films and metallic base layer is  $Y=C/B$  and the reflectivity of the circular polarizing mirror is

$$R = \left( \frac{\eta_0 B - C}{\eta_0 B + C} \right) \left( \frac{\eta_0 B - C}{\eta_0 B + C} \right)^* \quad (4)$$

and the reflection phase retardation is

$$\varphi = \arctg \left[ \frac{i\eta_0(CB^* - BC^*)}{(\eta_0^2 BB^* - CC^*)} \right] \quad (5)$$

where  $\eta_0$  is the equivalent conductance of the input medium. If equations (4) and (5) were used to calculate the corresponding values for S and P waves,  $R_s$ ,  $R_p$ ,  $\phi_s$ , and  $\phi_p$  would be obtained and the phase retardation  $\Delta\phi = \phi_s - \phi_p$  would be obtained.

The purpose of circular laser polarizing mirror is to have high reflection and appropriate phase retardation. Hence, one of its characteristics is that the film thickness is not quarter-wavelength thickness and the thicknesses for each layer are different and no periodicity can be found. However, this brings great difficulty into the calculation and manufacturing of film



system and makes high power laser circular polarizing mirror one of the most complicated devices of thin-film optical instrument.

The film system of circular polarizing mirror was designed on the computer with optimizing method. The optical thickness of the  $j$ -th layer was chosen as  $f_j \lambda_0 / 4$ , where  $f_j \in (0, 1.2)$  and was called the thickness parameter of the  $j$ -th layer,  $\lambda_0$  is the central wavelength ( $10.6 \mu\text{m}$  for  $\text{CO}_2$  laser). The target of calculation was to obtain a set of  $\{f_j\}$  so that within one wavelength of  $\lambda_0$  the film system will have high reflectivity and  $90^\circ$  phase retardation. Because of this need the following evaluation function was utilized

$$F = \sum_{\lambda} \left[ 1 - \frac{1}{2} (R_s + R_p) + \frac{|\pi/2 - |\Delta\phi||}{\pi/3} \right]^2 \quad (6)$$


When  $R_s = R_p = 1$ , and  $\Delta\phi = \pm\pi/2$  is established in the vicinity of  $\lambda_0$ , the value of  $F$  in equation (6) will become 0 and the ideal situation would be obtained. The actual computation goal was to find a minimum  $F$  for a set of  $\{f_j\}$ . This problem was optimized using non-linear resistance least square method. The attached table and figure show the typical  $f$  values and the relationship between the phase retardation and wavelength for a 14-layer structure for three sets of circular polarizing mirror systems with  $\text{Ag}$  as the substrate layer. Error analysis can also be carried out on the computer. The calculation showed that if the error of the thickness and refractivity were both  $\pm 1\%$  the error of  $\Delta\phi$  was  $\pm 5\%$ , and if the error of the thickness and refractivity were both  $\pm 2\%$ , the error of  $\Delta\phi$  would be  $\pm 12\%$ . When the error in

$\Delta\phi$  exceeded  $\pm 10\%$ . the applicability of circular polarizing mirror would deteriorate quickly. Therefore, the error in thickness and refractivity should be controlled within  $\pm 2\%$  during manufacturing. This requirement also implied that in the experiment the film thickness should be controlled accurately and the refractivity should be measured accurately.

Table: Calculated thickness parameter  $f$  for each layer of circular laser polarizing mirror

film no.	10-layer f value	12-layer f value	14-layer f value
1	0.713	0.724	0.742
2	0.694	0.708	0.714
3	0.586	0.588	0.596
4	0.741	0.752	0.763
5	0.783	0.791	0.806
6	0.857	0.863	0.872
7	0.932	0.934	0.936
8	0.931	0.956	0.962
9	0.958	0.967	0.968
10	0.964	0.968	0.972
11		0.983	0.991
12		0.987	0.993
13			1.080
14			0.996

note: Substrate was Ag, first layer facing atmosphere.

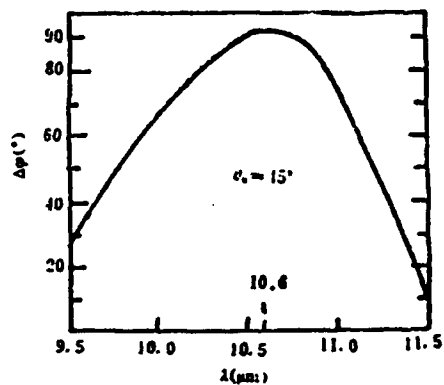

key: 1 - Figure: Relationship between phase retardation  $\Delta\phi$  and wavelength  $\lambda$  for the 14th layer mirror

### III. Experiment and Results

The experimental study of laser circular polarizing mirror was divided into film coating and testing. The coating was carried out by modifying DMDE-450 optical multiple-layer coating machine. Major improvements included installing a quartz-vibrating IC6000 film thickness monitor at an appropriate location within the vacuum chamber. From calculation and analysis in the previous section, it was learned that the key to the experiment was accurate measurement and control of film thickness and refractivity. Accurate control of the film thickness was achieved by combining optical thickness calibration and crystal vibration. The crystal vibration was first calibrated with high order optical thickness method and then the crystal vibration was used to monitor film thickness in real-time. In practicality, 40 layers of same material will be coated on the same control substrate using optical method and the corresponding relationship between the optical thickness and the physical thickness shown by crystal vibration would be established. After calibration of this manner, real-time monitoring of any film thickness by crystal vibration would be possible. An obvious advantage of this technique was that the monitoring wavelength between adjacent film layers could be compensated automatically and the error caused by change in molecular condensation characteristics could be avoided. After coating with the same material for 40 layers, even if the final layer showed 10% error the relative error for each single layer was only 0.25%, which is at least one order of

magnitude better than other optical calibration methods. Our experiment had shown that excellent results could be obtained with this technique and automatic coating process could be greatly improved. Accurate measurement of refractivity of the film was achieved with a high precision elliptical polarizing instrument.

The properties of manufactured laser circular polarizing mirror was characterized on a high power CO<sub>2</sub> laser device. After the output of a CO<sub>2</sub> laser device was directed through a initial polarizer, the laser beams were converted to polarized light which form a 45° angle with respect to the horizontal direction. The polarized light was reflected by a coated circular polarizing mirror and the reflected light was analyzed with a analytical polarizing mirror. The values of  $\Delta\phi$  and R can be calculated through the power values at different analytical polarizing angle. Measurement of this type is a relative measurement. Analysis has shown that errors incurred by the relative measurement were within  $\pm 2^\circ$  and  $\pm 1\%$  for  $\Delta\phi$  and R, respectively. The composite test results for the circular polarizing mirror manufactured in this study were: reflectivity  $R = (R_s + R_p)/2 \geq 98\%$ , phase retardation  $\Delta\phi = \phi_s - \phi_p = 90^\circ \pm 7^\circ$ , power density  $I \geq 1000 \text{ W/cm}^2$ . These three parameters would satisfy the requirement for circular polarizing mirrors for all industrial laser manufacturing process.

Based on the current technological level, equipment, and material supply in China, the first advanced laser circular

polarizing mirror since the 80's was manufactured. This achievement should provide a stimulus to bring up the level of laser research in China.

#### References

- [1] Olsen, F. O.: Cutting with polarized laser beams, 1st ed. Lyngby, Denmark; DVS, 1980, 197-200
- [2] Southwell W. H.: Appl. Opt., 1980, 19(16), 2688
- [3] Macleod H. A.: Thin film optical filters, 2nd ed., New York, Macmilian, 1986, 18-30

DISTRIBUTION LIST

DISTRIBUTION DIRECT TO RECIPIENT

<u>ORGANIZATION</u>	<u>MICROFICHE</u>
B085 DIA/RTS-2FI	1
C509 BALLOC509 BALLISTIC RES LAB	1
C510 R&T LABS/AVEADCOM	1
C513 ARRAADCOM	1
C535 AVRADCOM/TSARCOM	1
C539 TRASANA	1
Q592 FSTC	4
Q619 MSIC REDSTONE	1
Q008 NTIC	1
Q043 AFMIC-IS	1
E051 HQ USAF/INET	1
E404 AEDC/DOF	1
E408 AFWL	1
E410 ASDTC/IN	1
E411 ASD/FTD/TTIA	1
E429 SD/IND	1
P005 DOE/ISA/DDI	1
P050 CIA/OCR/ADD/SD	2
1051 AFTT/LDE	1
PO90 NSA/CDB	1
2206 FSL	1

Microfiche Nbr: FTD93C000459  
FTD-ID(RS)T-0101-93